


Client: Korea Petrochemical Ind. Co., Ltd.

Regression analysis according to ISO 9080 of the PE pipe grade P502BL

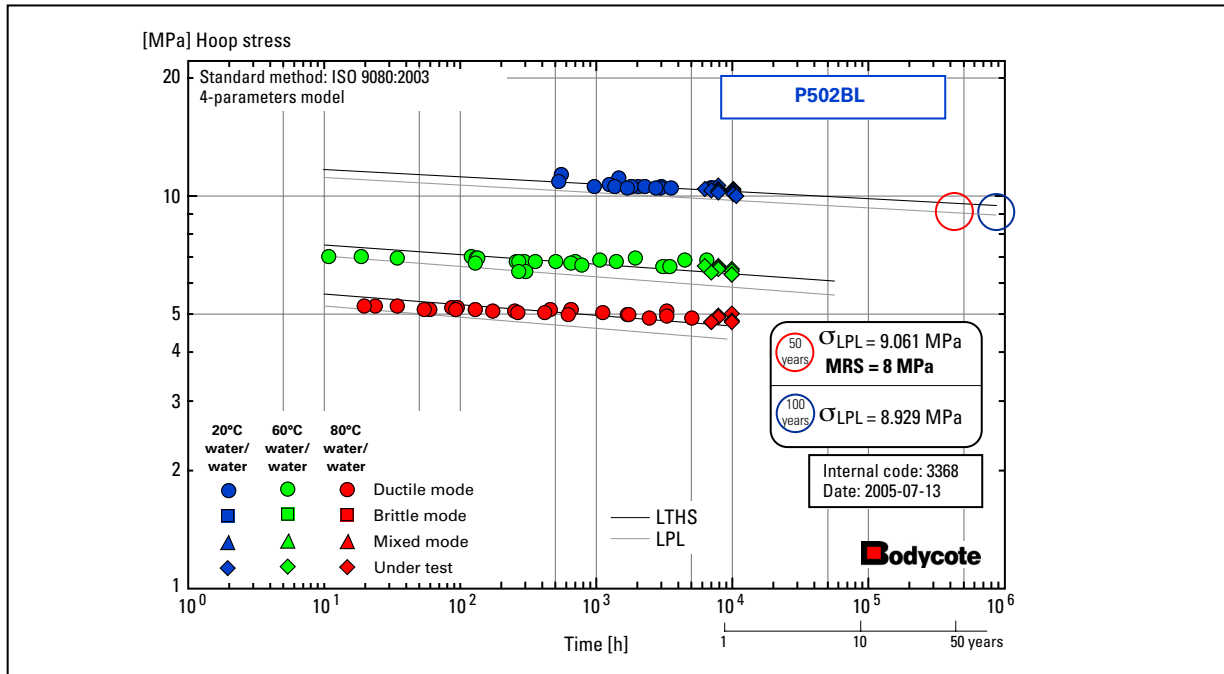

Introduction

Bodycote Polymer offers accredited testing and evaluation according to ISO 9080, i.e. hydrostatic pressure testing followed by evaluation of the long-term hydrostatic strength and MRS-classification according to ISO 12162.

Task

The aim was to use the Standard Extrapolation Method (SEM) according to ISO 9080:2003 in order to obtain a classification of the PE pipe grade P502BL from Korea Petrochemical Ind. Co., Ltd.

The work covers hydrostatic pressure testing at 20, 60 and 80°C and a SEM-evaluation according to ISO 9080:2003.

Results obtained

The evaluation was performed in accordance with ISO 9080:2003. The 4-parameters model gave the best fit.

Number of observations

20°C	60°C	80°C
30	34	30

Extrapolated strength values

Temp °C	Time yrs	σ_{LPL} MPa	σ_{LTHS} MPa
20	50.0	9.061	9.588
20	100	8.929	9.467
60	6.22	5.646	6.060
80	1.04	4.327	4.674

Classification: MRS = 8 MPa

Please contact us for further information!